

Reprinted from

# PHYSICA C

---

Physica C 226 (1994) 216-221

## Crystal chemistry of $\text{HgBa}_2\text{CaCu}_2\text{O}_{8+\delta}$ and $\text{HgBa}_2\text{Ca}_2\text{Cu}_3\text{O}_{8+\delta}$ Single-crystal X-ray diffraction results

L.W. Finger <sup>a</sup>, R.M. Hazen <sup>a,\*</sup>, R.T. Downs <sup>a</sup>, R.L. Meng <sup>b</sup>, C.W. Chu <sup>b</sup><sup>a</sup> *Geophysical Laboratory and Center for High Pressure Research, Carnegie Institution of Washington,  
5251 Broad Branch Road NW, Washington, DC 20015-1305, USA*<sup>b</sup> *Texas Center for Superconductivity, University of Houston, Houston, TX 77204-5932, USA*

Received 16 March 1994; revised manuscript received 14 April 1994

PHYSICA A, PHYSICA B, PHYSICA C and PHYSICA D are published by North-Holland (Elsevier Science B.V.), Amsterdam.

---

## PHYSICA C

### Editors:

**M.B. BRODSKY**, Argonne National Laboratory, Argonne, Illinois, USA  
**G.W. CRABTREE**, Argonne National Laboratory, Argonne, Illinois, USA  
**B.D. DUNLAP**, Argonne National Laboratory, Argonne, Illinois, USA  
**R.P. GRIESEN**, Natuurkundig Laboratorium, Vrije Universiteit, Amsterdam, The Netherlands  
**S. MAEKAWA**, Department of Applied Physics, Nagoya University, Nagoya, Japan  
**Yu.A. OSIPYAN**, Institute of Solid State Physics, Russian Academy of Sciences, Chernogolovka, Russia  
**H.R. OTT**, Laboratorium für Festkörperphysik, ETH, Zürich, Switzerland  
**S. TANAKA**, Superconductivity Research Laboratory, ISTEC, Tokyo, Japan  
(see preliminary pages for full addresses)

### Desk editors:

**P.J. HOFF**, Elsevier Science Publishers B.V., P.O. Box 103, 1000 AC Amsterdam, The Netherlands, Telephone: (020) 5862 568,  
Telefax: (020) 5862 704, Telex: 10704 espom nl  
**P.F. BAKKER**, as above, Telephone: (020) 5862 681

---

## Subscription data

Physica A (ISSN 0378-4371). For 1994, volumes 201-211 are scheduled for publication. Physica A is published semimonthly.  
Physica B (ISSN 0921-4526). For 1994, volumes 192-202 are scheduled for publication. Physica B is published monthly.  
Physica C (ISSN 0921-4534). For 1994, volumes 219-236 are scheduled for publication. Physica C is published two to three times per month.  
Physica D (ISSN 0167-2789). For 1994, volumes 70-78 are scheduled for publication. Physica D is published semimonthly.  
Subscription prices are available upon request from the publisher. A combined subscription to Physica A, Physica B, Physica C and Physica D is available at a reduced rate.

Subscriptions are accepted on a prepaid basis only and are entered on a calendar year basis. Issues are sent by surface mail except to the following countries where air delivery via SAL is ensured: Argentina, Australia, Brazil, Canada, China, Hong Kong, India, Israel, Japan, Malaysia, Mexico, New Zealand, Pakistan, Singapore, South Africa, South Korea, Taiwan, Thailand, USA. For all other countries airmail rates are available upon request.

Please address all your requests regarding orders and subscription queries to: Elsevier Science B.V., Journal Department, P.O. Box 211, 1000 AE Amsterdam, The Netherlands. Telephone: +31-20-5803642, Telefax: +31-20-5803598. Claims for issues not received should be made within six months of our publication (mailing) date.

Elsevier Science B.V. All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted in any form or by any means, electronic, mechanical, photocopying, recording or otherwise, without the prior written permission of the Publisher, Elsevier Science B.V., Copyright and Permissions Department, P.O. Box 521 1000 AM Amsterdam, The Netherlands.

*Special regulations for authors.* Upon acceptance of an article by the journal, the author(s) will be asked to transfer copyright of the article to the Publisher. This transfer will ensure the widest possible dissemination of information.

*Special regulations for readers in the USA.* This journal has been registered with the Copyright Clearance Center, Inc. Consent is given for copying of articles for personal or internal use, or for the personal use of specific clients. This consent is given on the condition that the copier pays through the Center the per-copy fee stated in the code on the first page of each article for copying beyond that permitted by Sections 107 or 108 of the US Copyright Law. The appropriate fee should be forwarded with a copy of the first page of the article to the Copyright Clearance Center, Inc., 27 Congress Street, Salem, MA 01970, USA. If no code appears in an article, the author has not given broad consent to copy and permission to copy must be obtained directly from the author. The fee indicated on the first page of an article in this issue will apply retroactively to all articles published in the journal, regardless of the year of publication. This consent does not extend to other kinds of copying, such as for general distribution, resale, advertising and promoting purposes, or for creating new collective works. Special written permission must be obtained from the Publisher for such copying. No responsibility is assumed by the Publisher for any injury and/or damage to persons or property as a matter of products liability, negligence or otherwise, or from any use or operation of any methods, products, instructions or ideas contained in the material herein.

US mailing notice - Physica C (ISSN 0921-4534) is published three times per month except semi-monthly in January, August, October and December (total 32 issues) by Elsevier Science B.V., Molenwerf 1, P.O. Box 211, 1000 AE Amsterdam, The Netherlands. Annual subscription price in the USA is US \$7578 (valid in North, Central and South America only), including air speed delivery. Second class postage paid at Jamaica, NY 11431.

USA POSTMASTERS: Send address changes to Physica C, Publications Expediting, Inc., 200 Meacham Avenue, Elmont, NY 11003. Airfreight and mailing in the USA by Publications Expediting.

Printed in The Netherlands



ELSEVIER

Physica C 226 (1994) 216–221

**PHYSICA C**

# Crystal chemistry of $\text{HgBa}_2\text{CaCu}_2\text{O}_{8+\delta}$ and $\text{HgBa}_2\text{Ca}_2\text{Cu}_3\text{O}_{8+\delta}$ Single-crystal X-ray diffraction results

L.W. Finger<sup>a</sup>, R.M. Hazen<sup>a,\*</sup>, R.T. Downs<sup>a</sup>, R.L. Meng<sup>b</sup>, C.W. Chu<sup>b</sup><sup>a</sup> *Geophysical Laboratory and Center for High Pressure Research, Carnegie Institution of Washington,  
5251 Broad Branch Road NW, Washington, DC 20015-1305, USA*<sup>b</sup> *Texas Center for Superconductivity, University of Houston, Houston, TX 77204-5932, USA*

Received 16 March 1994; revised manuscript received 14 April 1994

## Abstract

Crystal structures of  $\text{HgBa}_2\text{CaCu}_2\text{O}_{8+\delta}$  (Hg-1212) and  $\text{HgBa}_2\text{Ca}_2\text{Cu}_3\text{O}_{8+\delta}$  (Hg-1223) have been determined on single crystals at room temperature conditions by X-ray diffraction techniques. Both tetragonal specimens are isomorphous with compounds in the Tl–Ba–Ca–Cu–O system. We observe excess oxygen in both samples on two sites near the  $z=0$  plane: at  $(\frac{1}{2}00)$  and close to  $(\frac{1}{2}, 0.4, 0)$  – but no oxygen at  $(\frac{1}{2}\frac{1}{2}0)$  as reported in earlier studies. Refined Hg occupancies for both samples indicate a substitution of Cu for Hg of more than ten percent. If the substitution of Cu for Hg and excess O at  $(\frac{1}{2}00)$  are coupled, then the effect is to insert a perovskite-like six-coordinated copper site at (000). No evidence was found for a split atom at the barium sites in these compounds.

## 1. Introduction

The series of mercury-based superconductors,  $\text{HgBa}_2\text{Ca}_{n-1}\text{Cu}_n\text{O}_{2n+3}$ , are notable both for their relatively high critical temperatures [1–3] and the unique pressure dependence of the superconducting transition temperature [4–6]. Detailed structural information is essential to model the properties of these phases, to compare them with other copper-oxide superconductors, and to predict possible compositional variants with enhanced properties.

The mercury compounds are isomorphous with the well-known thallium compounds,  $\text{TlBa}_2\text{R}_{n-1}\text{Cu}_n\text{O}_{2n+3}$ . The Tl and Hg series differ primarily in oxygen occupancy of the (001) plane containing Tl or Hg, which is greater than 0.75 in the thallium compounds [7–10], but significantly less

than 0.5 in the mercury superconductors [1,4,11–13].

Several X-ray and neutron powder diffraction studies have revealed the basic structural characteristics of  $\text{HgBa}_2\text{CuO}_{4+\delta}$  (Hg-1201) [2,14–17] and  $\text{HgBa}_2\text{Ca}_2\text{Cu}_3\text{O}_{8+\delta}$  (Hg-1223) [13,17,18]. Structural questions remain, however, particularly regarding the locations of excess oxygen atoms, the possible substitution of copper for mercury as observed by Wagner et al. in Hg-1201 [11], and the split-atom model for barium in the latter structure proposed by Chmaissem et al. [13]. Furthermore, anisotropic thermal parameters, which may be important in modeling superconductivity at the relatively high temperatures of these samples, have not been reported previously.

The present study presents the first single-crystal X-ray data for  $\text{HgBa}_2\text{CaCu}_2\text{O}_{8+\delta}$  (Hg-1212) and Hg-1223 – measurements that provide insight on the crystal chemistry of these compounds.

\* Corresponding author.

## 2. Experimental

### 2.1. Sample description

The Hg-1212 and Hg-1223 samples investigated here were synthesized by the controlled vapor/solid reaction technique [19] by heating a precursor pellet of  $\text{Ba}_2\text{CaCu}_2\text{O}_x$  or  $\text{Ba}_2\text{Ca}_2\text{Cu}_3\text{O}_x$  (not compounds) and a composite Hg-source in an evacuated quartz tube. The precursor pellet was prepared by first dissolving appropriate amounts of  $\text{Ba}(\text{NO}_3)_2$ ,  $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$ , and  $\text{Cu}(\text{NO}_3)_2 \cdot 2\text{H}_2\text{O}$  in deionized water inside a beaker. The solution was slowly stirred, heated, and finally dried into a blue powder, which was removed from the beaker, ground, and placed in an alumina crucible. It was then slowly heated to between 500 and 550°C and kept at this temperature for 0.5 h, before being further heated to between 600 and 620°C, which temperature was maintained for 1 h. The resulting black mixture was then ground, compacted, and sintered in flowing oxygen at 900°C for 24 h.

These precursor pellets were either used immediately, or else they were stored in a desiccator for later use to minimize their exposure to humid air. Some of the pellets were placed in a glove box where they were pulverized, thoroughly mixed with HgO, and compacted to form the composite Hg-source. A small precursor pellet and a large composite Hg-source in a mass ratio of  $\sim 0.3$  were subsequently sealed in an evacuated quartz tube, which was in turn placed inside a welded stainless steel tube as a safety measure, heated to 800 to 850°C at a rate of 160°C/h, and kept at this temperature for 5–6 h before cooling to room temperature. The pellet was maintained at 300°C in flowing oxygen for 10 h for oxygenation. Critical temperatures for these two samples at room pressure are 127 and 134 K for Hg-1212 and Hg-1223, respectively.

Crushing of this material revealed an average grain size less than 10  $\mu\text{m}$  for both Hg-1212 and Hg-1223 specimens, though a few crystals up to 30  $\mu\text{m}$  maximum dimension was recovered. We examined a number of flat, rectangular crystals and selected euhedral specimens of Hg-1212 (approximately  $30 \times 30 \times 10 \mu\text{m}$ ) and of Hg-1223 (approximately  $25 \times 30 \times 8 \mu\text{m}$ ) for further study.

### 2.2. Data collection and refinement

Intensity data were collected on a Rigaku AFC-5 four-circle diffractometer equipped with a rotating-anode generator operated at 45 kV and 180 mA. We used graphite-monochromatized  $\text{Mo K}\alpha$  radiation ( $\lambda = 0.7093 \text{ \AA}$ ) to measure a hemisphere of data to  $(\sin \Theta)/\lambda = 0.71$ . Three reflections were monitored as orientation and intensity standards every 150 reflections, and they showed no significant variation during the data collection.

Most diffraction maxima for both Hg-1212 and Hg-1223 were broad, and many of the observed peaks were doublets, perhaps due to the stacking of multiple crystals in close alignment. One member of each split diffraction peak (presumably the component from the main crystal) was always well centered. These centered peaks were integrated using a new program that fit step-scan data to multiple constrained Gaussian doublets, corresponding to the  $\text{K}\alpha_1$ – $\text{K}\alpha_2$  wavelengths of the Mo source. When more than one doublet was present, only the central peak was retained. Peaks that appeared to be single but significantly exceeded the expected peak width (implying an unresolved doublet) were rejected by this procedure. These reflections were corrected for Lorentz polarization and absorption ( $\mu_1 = 367.7$  and  $325.0 \text{ cm}^{-1}$  for Hg-1212 and Hg-1223, respectively) effects and reduced to structure factors [20]. For Hg-1223, the crystal description was not sufficient and an empirical correction was also included. Reflections were averaged according to Laue group 4/mmm, which yielded 167 symmetrically distinct observations ( $I \geq 3\sigma$ ) for Hg-1212 ( $R_{\text{int}} = 0.032$ ), and 169 reflections for Hg-1223 ( $R_{\text{int}} = 0.048$ ); however, all 1693 observations were used in the refinement of the empirical absorption correction.

We initiated the structure refinements with parameters reported for thallium isomorphs [10]. Our refinements included a scale factor, variable atomic coordinates, and anisotropic thermal parameters for all fully-occupied sites. In addition, for both crystals we refined Cu occupancy of the Hg sites at (000), oxygen occupancy parameters for atoms at  $(\frac{1}{2} \frac{1}{2} 0)$  designated O3 in Hg-1212 and O4 in Hg-1223, and oxygen occupancies for atoms at  $(\frac{1}{2} 0 \approx 0)$  designated O4 and O5 in Hg-1212 and Hg-1223, respectively.

Refinements were performed with RFINE90, a

version of RFIN4 [21]. A weight of  $w = \sigma^{-2}(F_0)$  was assigned to each reflection, where  $\sigma F_0$  is the error derived from counting statistics, and the function,  $\sum w(|F_0| - |F_c|)^2$ , was minimized.

Initial refinement of Hg-1212 incorporated six atoms (Hg/Cu, Ba, Ca, Cu, O1, and O2) with isotropic temperature factors and an occupancy factor for the Hg/Cu site. We used this refinement to generate a difference Fourier map of the (001) plane at  $z=0$  (Fig. 1), in an effort to locate extra oxygen positions. Several previous studies have documented an O3 oxygen at  $(\frac{1}{2}\frac{1}{2}0)$  [13–16], while Wagner et al. observe a coupled substitution of copper for Hg plus extra oxygen at  $(\frac{1}{2}00)$  in Hg-1201 [11]. Our difference map reveals two prominent positive features. A maximum at  $(\frac{1}{2}00)$ , hereafter designated O4, corresponds to the oxygen position observed by Wagner et al.; we, too, observe significant Cu substitution on the Hg site. A second maximum at approximately  $(\frac{1}{2}, 0.40, 0)$  is close to, but distinct from, the previously reported partially filled "O3" at  $(\frac{1}{2}\frac{1}{2}0)$ . We propose that O3 is, in fact, a split atom. The Hg–O3 and Ba–O3 distances resulting from this off-centering of O3 are 2.46 and 2.83 Å, respectively.

Final refinement of Hg-1212 with twenty variable

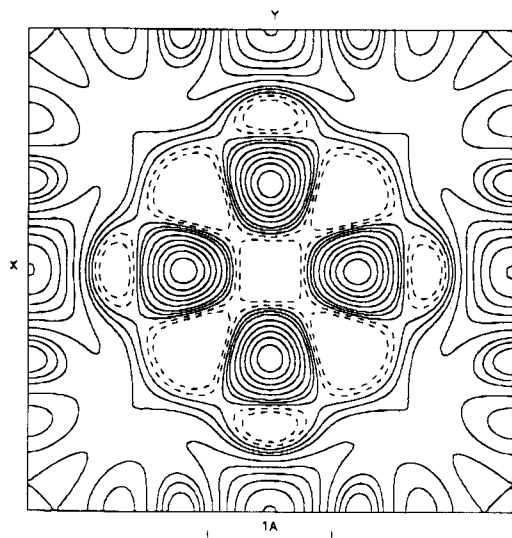


Fig. 1. Difference electron density map for the  $xy0$  section of Hg-1212. No defect oxygen sites are included in the calculated structure factors. Contour interval is approximately  $0.4 \text{ e}/\text{\AA}^3$ . The positive features at  $(\frac{1}{2}00)$  and  $(\frac{1}{2}, 0.4, 0)$ , the negative feature at  $(\frac{1}{2}\frac{1}{2}0)$  and the substitution of Cu for Hg are the basis for the defect model proposed.

parameters (one scale factor, one extinction parameter, five fractional coordinates, eight anisotropic thermal parameters for metal atoms, two isotropic temperature factors for oxygen, and occupancies for Hg, O3, and O4), based on 167 observed reflections, converged to a weighted  $R(R_w = \sigma^{-2}(F_0 - F_c)^2 / \sigma^{-2}F_0^2)$  of 0.035, and unweighted  $R(R = \sum ||F_0| - |F_c|| / \sum |F_0|)$  of 0.046. The goodness of fit for the converged refinement is 1.1. Refined positional, thermal parameters, and occupancies for Hg-1212 appear in Table 1.

Initial refinement of Hg-1223 without extra O4 and O5 oxygens at  $(\frac{1}{2}\frac{1}{2}0)$  and  $(\frac{1}{2}00)$ , respectively, was used to generate a difference Fourier as described above for Hg-1212. Positive features at  $(\frac{1}{2}, 0.40, 0)$  and  $(\frac{1}{2}00)$  were observed and included in subsequent refinements. The Hg-1223 refinement of 25 parameters, based on 1693 observations, converged to weighted  $R=0.069$  and unweighted  $R=0.092$ , with a goodness of fit = 2.0. Positional and thermal parameters are listed in Table 2. Refined occupancies of the Hg, O4, and O5 are strongly correlated to temperature factors and the O4 occupancy, furthermore, is inversely correlated to that of Hg. Refined values of these occupancies, therefore, are not quantitatively reliable. All refined models contain at least 10% Cu on the Hg site and at least 10% occupancy of O5. The refined O4 occupancy, however, varies from less than 1% for a model with 18% Cu on Hg, to 25% for a model with 10% Cu on Hg. Further constraints on Hg-1223 occupancies must await synthesis of im-

Table 1

Refined structural parameters for Hg-1212 at room temperature

Atom	$x$	$y$	$z$	$B$ (eq)	$\mu_{\parallel}/\mu_{\perp}$ <sup>a</sup>
Hg/Cu <sup>b</sup>	0	0	0	1.15(6)	0.77
Ba	$\frac{1}{2}$	$\frac{1}{2}$	0.2205(2)	0.65(5)	1.05
Ca	$\frac{1}{2}$	$\frac{1}{2}$	$\frac{1}{2}$	0.49(7)	0.67
Cu	0	0	0.3765(3)	0.46(6)	1.12
O1	0	$\frac{1}{2}$	0.3758(11)	0.4(2)	
O2	0	0	0.1553(18)	1.0(4)	
O3 <sup>c</sup>	$\frac{1}{2}$	0.40(4)	0	0.8 <sup>d</sup>	
O4 <sup>e</sup>	$\frac{1}{2}$	0	0	0.8	

<sup>a</sup>  $\mu_{\parallel}/\mu_{\perp}$  is the ratio of the rms amplitudes of vibration parallel and perpendicular to the  $c$  axis.

<sup>b</sup> Refined Cu occupancy = 0.13(2).

<sup>c</sup> Refined O3 occupancy = 0.10(3).

<sup>d</sup> Isotropic temperature factors for O3 and O4 are fixed.

<sup>e</sup> Refined O4 occupancy = 0.12(5).

Table 2  
Refined structural parameters for Hg-1223 at room temperature

Atom	<i>x</i>	<i>y</i>	<i>z</i>	<i>B</i> (eq)	$\mu_{\parallel}/\mu_{\perp}$ <sup>a</sup>
Hg/Cu <sup>b</sup>	0	0	0	1.29(4)	1.12
Ba	$\frac{1}{2}$	$\frac{1}{2}$	0.17491(8)	0.68(2)	1.11
Ca	$\frac{1}{2}$	$\frac{1}{2}$	0.39758(28)	0.50(6)	1.43
Cu1	0	0	$\frac{1}{2}$	0.43(5)	1.67
Cu2	0	0	0.30068(17)	0.41(4)	1.95
O1	0	$\frac{1}{2}$	$\frac{1}{2}$	0.3(2)	
O2	$\frac{1}{2}$	0	0.3060(7)	0.9(5)	
O3	0	0	0.1228(12)	1.7(7)	
O4 <sup>c</sup>	$\frac{1}{2}$	0.36 <sup>d</sup>	0	0.8 <sup>e</sup>	
O5 <sup>f</sup>	$\frac{1}{2}$	0	0	0.8	

<sup>a</sup>  $\mu_{\parallel}/\mu_{\perp}$  is the ratio of the rms amplitudes of vibration parallel and perpendicular to the *c* axis.

<sup>b</sup> Refined Cu occupancy = 0.18(1).

<sup>c</sup> Refined O4 occupancy = 0.00(2).

<sup>d</sup> *y* coordinate of O4 fixed at value determined from difference electron density map.

<sup>e</sup> Isotropic temperature factors for O4 and O5 are fixed.

<sup>f</sup> Refined O5 occupancy = 0.13(5).

Table 3  
Selected interatomic distances (Å) and Cu–O–Cu angles for Hg-1212 and Hg-1223 at room temperature

Bond	Hg-1212	Bond	Hg-1223
Hg–O2[2]	1.97(2)	Hg–O3[2]	1.975(19)
Hg–O3[4]	2.46(8)	Hg–O4[4]	2.4(1)
Ba–O1[4]	2.757(10)	Ba–O2[4]	2.824(8)
Ba–O2[4]	2.848(7)	Ba–O3[4]	2.837(5)
Ba–O3[1]	2.83(2)	Ba–O4[1]	2.81(2)
Ca–O1[8]	2.490(9)	Ca–O1[4]	2.516(3)
		Ca–O2[4]	2.413(7)
Cu–O1[4]	1.928(1)	Cu1–O1[4]	1.927(1)
Cu–O2[1]	2.81(2)	Cu2–O2[4]	1.929(1)
		Cu2–O3[1]	2.78(2)
Cu–O1–Cu	179.5(9)	Cu2–O2–Cu2	175.4(7)

proved crystals or higher-resolution powder diffraction data.

Calculated and observed structure factors are available from the authors.

### 3. Results and discussion

#### 3.1. Structure of HgBa<sub>2</sub>CaCu<sub>2</sub>O<sub>6+δ</sub>

All known members of the mercury superconductor series have tetragonal unit cells. We measured unit

cells for two Hg-1212 crystals (one crystal with  $a=3.8554(10)$  Å,  $c=12.693(7)$  Å,  $V=188.66(13)$  Å<sup>3</sup>; and the crystal used in intensity measurements with  $a=3.8564(9)$  Å,  $c=12.682(4)$  Å,  $V=188.60(9)$  Å<sup>3</sup>), giving a calculated density of 6.36 g/cm<sup>3</sup>.

Copper–oxygen, calcium–oxygen, and barium–oxygen bond distances in HgBa<sub>2</sub>CaCu<sub>2</sub>O<sub>6+δ</sub> are similar to those observed in the isostructural compound TlBa<sub>2</sub>CaCu<sub>2</sub>O<sub>7</sub> [10,22]. The principal differences occur in the substitution of Hg (and Cu) for Tl at (000), and partial occupancy of O3 at ( $\frac{1}{2}$ , 0.40, 0). In the thallium compound the oxygen site at ( $\frac{1}{2}$ ,  $\frac{1}{2}$ , 0) is fully occupied, but in the mercury analogs the site is significantly less than half occupied – 0.10(3) in our sample. Thus thallium is six-coordinated, while mercury is effectively two-coordinated. One consequence of this coordination difference is that the Hg–O2 distance (parallel to *c*) is shorter than the Tl–O distance (1.97(2) Å for Hg–O2 compared to more than 2.00 Å for Tl–O2). The mercury compound thus displays a slightly shorter *c* axis than the thallium isomorph [22].

The Hg site in our sample incorporates 0.13(2) Cu – an amount balanced by the 0.12(5) oxygen atoms in the O4 site at ( $\frac{1}{2}$ , 0, 0). The *z* coordinate of O4 may deviate slightly from 0.00, but not by more than 0.4 Å, based on electron density maps.

#### 3.2. Structure of HgBa<sub>2</sub>Ca<sub>2</sub>Cu<sub>3</sub>O<sub>8+δ</sub>

The Hg-1223 unit cell is  $a=3.842(5)$  Å,  $c=15.832(8)$  Å,  $V=233.58(44)$  Å<sup>3</sup>, giving a calculated density of 6.21 g/cm<sup>3</sup>.

Copper–oxygen and calcium–oxygen bond distances are typical of other 1223-type superconductors [10], while these distances and those of Hg–O agree closely with room-temperature values reported by Chmaissem et al. [13] based on neutron powder diffraction. In particular, we observe in-plane Cu1–O1 and Cu2–O2 distances of 1.927(1) and 1.929(1) Å, respectively, compared to 1.925 for both distances reported by Chmaissem et al. We observe mean Ca–O, Hg–O3, and Hg–O4 of 2.452(5), 1.97(2), and 2.4(1) Å, compared to 2.493(6), 1.95(1), and 2.7225(1) for the neutron study. The Hg–O3 bond, which is parallel to the *c* axis, is significantly shorter than the Tl–O3 distance (greater than 2.0 Å) ob-

served in the thallium isomorph [10]. The relatively short Hg–O distances in both mercury compounds of this study point to stronger interlayer coupling, which may contribute to the unusually high  $T_c$ .

Observed barium–oxygen distances conform to those of  $TlBa_2Ca_2Cu_3O_9$ : approximately 2.83 Å in both samples [8]. These Ba–O distances, however, are significantly different from values reported by Chmaissem et al. [13], who suggest that Ba may be modeled as a split atom with approximately half Ba displaced by 0.25 Å above and below the centric position,  $(\frac{1}{2}\frac{1}{2}z)$ . We observe no evidence for this splitting in refinements of single-crystal X-ray data. In fact, anisotropic temperature parameters are well behaved and reveal near-isotropic barium vibration with relatively small rms displacements, typical of nine-coordinated Ba in other oxides. These discrepancies between X-ray single crystal and neutron powder data may reflect differences in sample order.

Refined anisotropic thermal parameters reveal that the motions of mercury, calcium, barium, and oxygen atoms are close to isotropic, probably reflecting the uniform coordination of these atoms. Ratios of maximum to minimum vibration amplitudes for these atoms are less than 1.5. The two symmetrically distinct copper atoms, on the other hand, display elongated thermal motion parallel to [001] with atom displacements approaching two times greater parallel to  $c$  than parallel to  $a$  – an anisotropy typical of that observed in other structures with square-planar cation coordination.

### 3.3. Revised structural formulae for Hg superconductors

The observation by Wagner et al. and us of coupled substitution of approximately equal amounts of Cu for Hg at (000) and O on a new site at  $(\frac{1}{2}00)$ , requires a structural formula that acknowledges the presence of excess oxygen on two distinct sites. Our sample of Hg-1212, for example, may be described as:  $(Hg_{0.87}Cu_{0.13})Ba_2CaCu_2O_{6.22}$ . But, in more general terms, two oxygen  $\delta$  terms are required:  $(Hg_{1-\delta_1}Cu_{\delta_1})Ba_2CaCu_2O_{6+\delta_1+\delta_2}$ , where  $\delta_1$  and  $\delta_2$  represent the fractional occupancies of oxygen at  $(\frac{1}{2}00)$  and  $(\frac{1}{2}, 0.40, 0)$ , respectively. Further structural investigations, coupled with synthesis and ana-

lytical studies, will be required to resolve the details of this complex system.

Although the diffraction data for these experiments do not have the quality required to answer all questions regarding defect structures, the equality between the amount of Cu substitution in the Hg position and the amount of O at  $(\frac{1}{2}00)$  is suggestive of partial substitution of a perovskite-like, octahedrally coordinated, Cu layer in both Hg-1212 and Hg-1223 samples. Because the substitution of Cu for Hg is not found in some studies [14,15], this effect may be due to some aspect of the synthesis. Alternatively, the distinctive characteristics of our sample may reflect the selection of the largest, most regular – and therefore possibly atypical – single crystals in otherwise fine-grained samples.

### Acknowledgements

We acknowledge the important contributions of J.D. Jorgensen and an anonymous reviewer of an earlier version of this manuscript. Crystal synthesis was performed at the Texas Center for Superconductivity, which is jointly supported by NSF grant DMR 91-22045 and USAFOSR Grant F49620-93-1-0310 by BMDO, and the State of Texas. X-ray diffraction work at the Geophysical Laboratory is supported by NSF grant EAR92-18845 and by the Carnegie Institution of Washington.

### References

- [1] S.N. Putilin, E.V. Antipov, O. Chmaissem and M. Marezio, *Nature* 362 (1993) 226.
- [2] A. Schilling, M. Cantoni, J.D. Gao and H.R. Ott, *Nature* 363 (1993) 56.
- [3] Z.J. Huang, R.L. Meng, X.D. Qui, Y.Y. Sun, J. Kulik, Y.Y. Xue and C.W. Chu, *Physica C* 217 (1993) 1.
- [4] C.W. Chu, L. Gao, F. Chen, Z.J. Huang, R.L. Meng and Y.Y. Xue, *Nature* 365 (1993) 323.
- [5] M. Nunez-Regueiro, J.L. Tholence, E.V. Antipov, J.J. Capponi and M. Marezio, *Science* 262 (1993) 97.
- [6] L. Gao, Y.Y. Xue, F. Chen, Q. Xiong, R.L. Meng, D. Ramirez, C.W. Chu, J.H. Eggert and H.K. Mao, *Phys. Rev. Lett.* (1994), in press.
- [7] S.S.P. Parkin, V.Y. Lee, A.I. Nazzari, R. Savoy, R. Beyers and S. LaPlaca, *Phys. Rev. Lett.* 61 (1988) 750.
- [8] B. Moroson, D.S. Ginley, J.E. Schirber and E.L. Venturini, *Physica C* 156 (1988) 587.

- [9] M.A. Subramanian, J.C. Calabrese, C.C. Torardi, J. Gopalakrishnan, T.R. Askew, R.B. Flippen, K.J. Morrissey, U. Chowdhry and A.W. Sleight, *Nature* 332 (1988) 420.
- [10] R.M. Hazen, in: *Physical Properties of High Temperature Superconductors*, Vol. 2, ed. D.M. Ginsberg (1990) p. 121.
- [11] J.L. Wagner, P.G. Radaelli, D.G. Hinks, J.D. Jorgensen, J.F. Mitchell, B. Dabrowski, G.S. Knapp and M.A. Beno, *Physica C* 210 (1993) 447.
- [12] O. Chmaissem, Q. Huang, S.N. Putilin, M. Marezio and A. Santoro, *Physica C* 212 (1993) 259.
- [13] O. Chmaissem, Q. Huang, E.V. Antipov, S.N. Putilin, M. Marezio, S.M. Loureiro, J.J. Capponi, J.L. Tholence and A. Santoro, *Physica C* 217 (1994) 265.
- [14] P.G. Radaelli, J.L. Wagner, B.A. Hunter, M.A. Beno, G.S. Knapp, J.D. Jorgensen and D.G. Hinks, *Physica C* 216 (1993) 29.
- [15] E.V. Antipov, J. Capponi, C. Chaillout, O. Chmaissem, S.M. Loureiro, M. Marezio, S.N. Putilin, A. Santoro and J.L. Tholence, *Physica C* 218 (1993) 348.
- [16] Q. Huang, J.W. Lynn, R.L. Meng and C.W. Chu, *Physica C* 218 (1993) 356.
- [17] B.A. Hunter, J.D. Jorgensen, J.L. Wagner, P.G. Raedelli, D.G. Hinks, H. Shaked, R.L. Hitterman and R.B. VonDreele, *Physica C* 221 (1994) 1.
- [18] E.V. Antipov, S.M. Loureiro, C. Chaillout, J.J. Capponi, P. Bordet, J.L. Tholence, S.N. Putilin and M. Marezio, *Physica C* 215 (1993) 1.
- [19] R.L. Meng, L. Beauvais, Z.N. Zhang, Z.J. Huang, Y.Y. Sun, Y.Y. Xue and C.W. Chu, *Physica C* 216 (1993) 21.
- [20] C.W. Burnham, *Am. Mineral.* 51 (1966) 159.
- [21] L.W. Finger and E. Prince, *Natl. Bur. Standards Tech. Note* 854 (1975) p. 128.
- [22] B. Morosin, D.S. Ginley, P.F. Hlava, M.J. Carr, R.J. Baughman, J.E. Schirber, E.L. Venturini and J.F. Kwak, *Physica C* 152 (1988) 413.



# 1994 PHYSICS and MATERIALS SCIENCE JOURNALS

## Applied Surface Science

Volumes 72-81 in 40 issues. Price: US \$ 2114.00 / Dfl. 3910.00

## Astroparticle Physics

Volume 2 in 4 issues. Price: US \$ 182.00 / Dfl. 336.00

## Computational Materials Science

Volume 2 in 4 issues. Price: US \$ 211.00 / Dfl. 391.00

## Computer Physics Communications

Volumes 79-85 in 21 issues. Price: US \$ 2236.00 / Dfl. 4137.00

## International Journal of Applied

### Electromagnetics in Materials

Volume 5 in 4 issues. Price: US \$ 203.00 / Dfl. 376.00

## Journal of Crystal Growth

Volumes 135-145 in 44 issues. Price: US \$ 4822.00 / Dfl. 8921.00

## Journal of Geometry and Physics

Volumes 13 and 14 in 8 issues. Price: US \$ 358.00 / Dfl. 662.00

## Journal of Luminescence

Volumes 59-62 in 24 issues. Price: US \$ 1083.00 / Dfl. 2004.00

## Journal of Magnetism and Magnetic Materials

Volumes 126-137 in 36 issues. Price: US \$ 3347.00 / Dfl. 6192.00

## Journal of Non-Crystalline Solids

Volumes 162-176 in 45 issues. Price: US \$ 3535.00 / Dfl. 6540.00

## Journal of Nuclear Materials

Volumes 206-216 in 33 issues. Price: US \$ 3098.00 / Dfl. 5731.00

## Materials Letters

Volumes 19-22 in 24 issues. Price: US \$ 899.00 / Dfl. 1664.00

## Nuclear Instruments and Methods in Physics Research - Section A

Accelerators, Spectrometers, Detectors & Associated Equipment

Volumes 337-351 in 45 issues. Price: US \$ 5441.00 / Dfl. 10,065.00

## Nuclear Instruments and Methods in Physics Research - Section B

Beam Interactions with Materials and Atoms

Volumes 83-94 in 48 issues. Price: US \$ 4352.00 / Dfl. 8052.00

*Reduced combined 1994 subscription price* to Nuclear Instruments and Methods - A and B: US \$ 9063.00 / Dfl. 16,767.00

## Nuclear Physics A

Volumes 566-580 in 60 issues. Price: US \$ 4792.00 / Dfl. 8865.00

## Nuclear Physics B

Volumes 409-432 in 72 issues. Price: US \$ 7537.00 / Dfl. 13,944.00

## Nuclear Physics B - Proceedings Supplements

Volumes 34-38 in 15 issues. Price: US \$ 881.00 / Dfl. 1630.00

*Reduced combined 1994 subscription price* to Nuclear Physics A + Nuclear Physics B + NPB-Proceedings Supplements: US \$ 11,202.00 / Dfl. 20,724.00

## Optical Materials

Volume 3 in 4 issues. Price: US \$ 206.00 / Dfl. 381.00

## Optics Communications

Volumes 103-111 in 54 issues. Price: US \$ 2121.00 / Dfl. 3924.00

## Physica A - Statistical and Theoretical Physics

Volumes 201-211 in 44 issues. Price: US \$ 2503.00 / Dfl. 4631.00\*

## Physica B - Condensed Matter Physics

Volumes 192-202 in 44 issues. Price: US \$ 2503.00 / Dfl. 4631.00\*

## Physica C - Superconductivity

Volumes 219-236 in 72 issues. Price: US \$ 4096.00 / Dfl. 7578.00\*

## Physica D - Nonlinear Phenomena

Volumes 70-78 in 36 issues. Price: US \$ 2048.00 / Dfl. 3789.00\*

*\*Reduced rates are available for combined subscriptions to Physica; please contact the publisher for details.*

## Physics Letters A

Volumes 185-197 in 78 issues. Price: US \$ 2537.00 / Dfl. 4693.00

## Physics Letters B

Volumes 317-340 in 96 issues. Price: US \$ 4683.00 / Dfl. 8664.00

## Physics Reports

Volumes 240-251 in 72 issues. Price: US \$ 2342.00 / Dfl. 4332.00

*Reduced combined 1994 subscription price* to Physics Letters A, Physics Letters B + Physics Reports: US \$ 8502.00 / Dfl. 15,729.00

## Solid State Ionics

Volumes 68-76 in 36 issues. Price: US \$ 1805.00 / Dfl. 3339.00

## Surface Science

(including Surface Science Letters)

Volumes 296-318 in 69 issues. Price: US \$ 6104.00 / Dfl. 11,293.00

## Surface Science Reports

Volume 18-20 in 24 issues. Price: US \$ 618.00 / Dfl. 1143.00

*Reduced combined 1994 subscription price* to Surface Science (including Surface Science Letters), Applied Surface Science and Surface Science Reports: US \$ 8192.00 / Dfl. 15,156.00

## Ultramicroscopy

Volumes 52-56 in 20 issues. Price: US \$ 1151.00 / Dfl. 2130.00

*Dutch Guilder price(s) quoted applies worldwide, except in the Americas (North, Central and South America). US Dollar price(s) quoted applies in the Americas only. Journals are sent by Surface Mail to all countries except to the following where Air Delivery via SAL mail is ensured at no extra cost to the subscriber: Argentina, Australia/New Zealand, Brazil, Hong Kong, India, Israel, Japan, Malaysia, Mexico, Pakistan, P.R. China, Singapore, S. Africa, S. Korea, Taiwan, Thailand, USA & Canada. Customers in the European Community should add the appropriate VAT rate applicable in their country to the price(s).*



## ELSEVIER SCIENCE B.V.

P.O. Box 103, 1000 AC Amsterdam, The Netherlands

Elsevier Science Inc., Journal Information Center, PO Box 882,  
Madison Square Station, New York, NY 10159, U.S.A.