

Eight new high-temperature superconductors with the 1:2:4 structure

Donald E. Morris, Janice H. Nickel, John Y. T. Wei, Naggi G. Asmar, Jeffrey S. Scott,
Ulrich M. Scheven, Charles T. Hultgren, and Andrea G. Markelz
Physics Division, Lawrence Berkeley Laboratory, Berkeley, California 94720

Jeffrey E. Post

Smithsonian Institution, National Museum of Natural History, Washington, D.C. 20560

Peter J. Heaney and David R. Veblen

Department of Earth and Planetary Sciences, The Johns Hopkins University, Baltimore, Maryland 21218

Robert M. Hazen

Geophysical Laboratory, Carnegie Institution of Washington, Washington, D.C. 20008

(Received 4 October 1988; revised manuscript received 14 November 1988)

New high-temperature superconducting compounds $RBa_2Cu_4O_8$ ($R = Nd, Sm, Eu, Gd, Dy, Ho, Er,$ and Tm) which share the 1:2:4 structure of $YBa_2Cu_4O_8$ are bulk synthesized using a new high-pressure oxygen technique. All compounds show substantial Meissner diamagnetism [$(3-25) \times 10^{-4}$ emu/g at 20 K]. Critical temperatures (57–81 K) vary inversely with ion size (opposite to 1:2:3), and directly with orthorhombic distortion (which is much smaller than in corresponding 1:2:3 compounds). $R_2Ba_4Cu_7O_x$ compounds (with alternating blocks of 1:2:3 and 1:2:4) were also prepared. The variable oxygen stoichiometry of 1:2:3 is not shared by the 1:2:4 compounds.

The number of known high-temperature superconducting compounds is growing steadily,¹⁻⁴ yet there is no clear consensus on relationships among crystal structure, electronic configuration, and other key physical properties. We propose a new avenue to synthesis of additional high-temperature superconductors. It is well known that the superconducting cuprates are very highly oxidized compounds (the original $La_{1.85}Sr_{0.15}CuO_4$ superconductor has an average Cu valency of 2.15, while in $YBa_2Cu_3O_7$ the value is 2.33) and tend to lose oxygen when heated, e.g., during synthesis. Processing in concentrated oxygen (high-pressure oxygen gas) can prevent this oxygen loss, and will thermodynamically favor the formation of highly oxidized phases, which may be new superconductors.

To demonstrate this principle, we have synthesized the high-temperature superconductor $YBa_2Cu_4O_8$ and eight new rare-earth compounds $RBa_2Cu_4O_8$ ($R = Nd, Sm, Eu, Gd, Dy, Ho, Er,$ and Tm). $YBa_2Cu_4O_8$ was sintered in high-pressure oxygen [$P(O_2) \approx 120$ atm] for 8 h at 930 °C using a commercial high-pressure oxygen furnace.⁵ Preparation of the rare-earth compounds required differing synthesis temperatures and pressures.⁶ Bulk superconductivity was demonstrated by substantial Meissner diamagnetism, with $\chi \approx -25 \times 10^{-4}$ emu/g for $YBa_2Cu_4O_8$ at 20 K, corresponding to $\sim 20\%$ volume diamagnetism (see Table I and Fig. 1).

The 1:2:4 compounds are thermodynamically stable in high- $P(O_2)$, because the alternative 1:2:3 phase ($RBa_2Cu_3O_{7-\delta}$) loses oxygen upon heating to processing temperature. These new compounds comprise the first set of isostructural, stoichiometric (i.e., with well-constrained oxygen content) superconductors, and thus they are an ideal system to study effects of small structural variations on superconducting properties. Their critical tempera-

tures range from 57 to 81 K and vary with structural parameters (see Fig. 5). The oxygen high-pressure synthesis technique can also produce the 2:4:7 compounds $R_2Ba_4Cu_7O_{15-x}$ in which 1:2:3 and 1:2:4 layers alternate along the c axis. P - T - x phase-stability diagrams will be published elsewhere.⁶

The 1:2:4 structure had first been observed as intergrowth in $YBa_2Cu_3O_{7-\delta}$ (the 1:2:3 compound) as planar defects in which a second CuO layer is introduced between the BaO layers, increasing the Y-Y distance from 11.7 to 13.6 Å.^{7,8} Because the positions of Cu in the Cu-O layers differ by $a/2$ along the a axis,⁸ c is doubled to $2 \times 13.6 = 27.2$ Å.⁹ Epitaxial thin films were made with

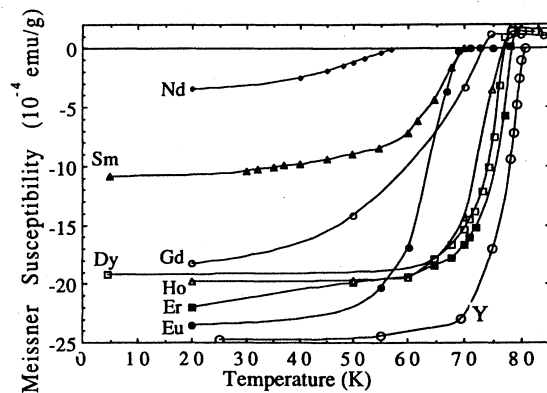


FIG. 1. Meissner susceptibility curves of superconducting compounds $RBa_2Cu_4O_8$ ($R = Y, Nd, Sm, Eu, Gd, Dy, Ho, Er$). The transitions are strong and sharp. T_c 's differ and are correlated with ion size, lattice parameters, and orthorhombic distortion (see Fig. 5).

TABLE I. Superconducting and structural parameters of $R\text{Ba}_2\text{Cu}_4\text{O}_8$ compounds. Parentheses denote uncertainties indicated by Rietveld refinement. Square brackets are values for the 2:4:7 phase.

| <i>R</i> | Superconducting parameters ^a | | | Phases present ^d | | | Lattice parameters ^e of 1:2:4 phase (2:4:7 phase) | | | | |
|----------|---|----------------------------------|---------------------------------------|-----------------------------|-------|-------|--|--------------|--------------|----------------------------|------------|
| | T_c (K) | $\chi_{20\text{K}}$ ^b | $4\rho\chi_{20\text{K}}$ ^c | 1:2:3 | 2:4:7 | 1:2:4 | <i>a</i> (Å) | <i>b</i> (Å) | <i>c</i> (Å) | <i>V</i> (Å ³) | <i>b/a</i> |
| Y | 80.4 ± 0.2 | -25 | 20% | no | no | all | 3.8395(2) | 3.8703(2) | 27.231(1) | 404.7 | 1.0080 |
| Nd | ~57 | -3.5 | 3% | trace | no | minor | | | ~27.3 | | |
| Sm | 69.3 ± 0.4 | -11 | 10% | 70% | no | 30% | 3.872(1) | 3.886(1) | 27.308(5) | 410.9 | 1.0036 |
| Eu | 68.9 ± 0.4 | -24 | 21% | no | 40% | 60% | 3.8650(6) | 3.8837(5) | 27.279(4) | 409.5 | 1.0048 |
| | | | | | | | [3.879(2)] | [3.886(1)] | [50.39(3)] | [759.6] | [1.0018] |
| Gd | 73.4 ± 1.2 | -18 | 16% | no | 60% | 40% | 3.863(1) | 3.881(7) | 27.259(5) | 408.7 | 1.0047 |
| | | | | | | | [3.872(1)] | [3.879(1)] | [50.36(2)] | [756.4] | [1.0018] |
| Dy | 77.2 ± 0.1 | -19 | 17% | no | no | all | 3.8463(3) | 3.8726(3) | 27.237(1) | 405.7 | 1.0068 |
| Ho | 77.4 ± 0.6 | -20 | 18% | no | no | all | 3.8404(6) | 3.8704(6) | 27.221(5) | 404.6 | 1.0078 |
| Er | 78.3 ± 0.2 | -22 | 20% | no | no | all | 3.8366(5) | 3.8685(5) | 27.230(4) | 404.1 | 1.0083 |
| Tm | 78.6 ± 0.3 | -11 | 10% | no | no | all | 3.827(1) | 3.864(1) | 27.18(1) | 401.9 | 1.0097 |

^aBy observation of bulk diamagnetism. The T_c 's correlate with lattice parameters *a* and *b*, and with orthorhombic distortion (see Fig. 5).

^bFlux expulsion on cooling to 20 K in a constant 6-Oe field, in units of 10^{-4} emu/g.

^cDiamagnetic volume fraction, neglecting expelled flux trapped in pores. The density ρ is calculated from the unit-cell volume.

^dRelative amounts estimated from x-ray powder-diffraction patterns and Rietveld refinements.

^eThe Rietveld procedure was used and a sample displacement correction was refined along with the unit-cell parameters. The refinement included 1:2:3 or 2:4:7 phases when present. The unit-cell parameters found for the Dy compound did not differ significantly from those determined using a Cr_2O_3 internal standard.

1:2:4 as a distinct,⁹ or majority phase^{10,11} with $T_c \sim 80$ K, but bulk 1:2:4 material could not be prepared. X-ray diffraction on films¹¹ gave approximate lattice parameters, but orthorhombic distortion, oxygen locations, and fractional site occupation could not be determined in the absence of bulk specimens.

Our bulk samples, prepared in high- $P(\text{O}_2)$, were confirmed as 1:2:4 by electron diffraction (Fig. 2), transmission electron microscopy (TEM) (Fig. 3), and x-ray powder diffraction (XPD) (Fig. 4). The lattice parameters of $\text{YBa}_2\text{Cu}_4\text{O}_8$ are $a = 3.8395(2)$ Å, $b = 3.8703(2)$ Å, $c = 27.231(1)$ Å, in general agreement with Ref. 11 but with higher precision. The average value of the *a* and *b* crystallographic axes (3.855 Å) is close to that of 1:2:3 in both its orthorhombic (3.853 Å) and tetragonal (3.857 Å) variants,¹² but the axial ratio $b/a = 1.008$ corresponds to distortion less than half that in fully oxidized $\text{YBa}_2\text{Cu}_3\text{O}_7$ ($b/a = 1.017$).

All phases in the polycrystalline samples appear black and optically opaque, with average grain sizes ≤ 1 μm. Electron microanalyses of samples in the Y-Ba-Cu-O system were obtained on a JSM model 35 scanning electron microscope (SEM), (20 kV, 0.01-μA beam current, 2.5-μm spot size). Standards include pure Cu metal, NBS microprobe standard K253 for Ba, and Y standard REE3 as described in Ref. 13. Portions of ceramic-disk samples were embedded in epoxy cement and polished for microprobe analysis. SEM of the polished surface revealed smooth areas suited for electron microanalysis, as well as considerable intergranular porosity characteristic of ceramic superconductors.

The predominant phase is a ternary oxide with cation ratios of Y:Ba:Cu close to 1:2:4. Though a few analyses yielded only 3.7 to 3.8 Cu per three Y+Ba, no analyses close to a 1:2:3 stoichiometry were obtained. Occasional

grains of a yttrium cuprate and a barium cuprate, both with 1:1 cation ratios, were observed. The powder-diffraction pattern for $\text{YBa}_2\text{Cu}_4\text{O}_8$ shows minor amounts of Ba cuprate and an unidentified phase (peaks at 7.49, 3.09, and 3.00 Å), but no evidence of a 1:2:3 component. Thus, we conclude that the 1:2:4 compound is the predominant bulk superconductor in these samples. However, the calculated intensity of the diagnostic 11.7-Å line for the Y-bearing 1:2:3 compound is relatively weak (4.2%), so trace amounts of it cannot be ruled out.

Calculated powder patterns for 1:2:3 phases show that the intensity of the 11.7-Å peak increases with increasing atomic number from a relative intensity 4.2% for Y to 33% for Eu and Gd. Therefore, even very minor quanti-

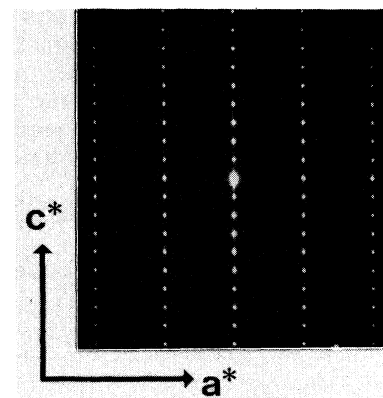


FIG. 2. A *b*-axis selected-area electron diffraction pattern of $\text{YBa}_2\text{Cu}_4\text{O}_8$, indicating that most of this phase is well ordered. Minor diffuse streaking parallel to c^* indicates that some crystals possess some structural disorder affecting the periodicity of the $(00\bar{l})$ planes (see Fig. 3).

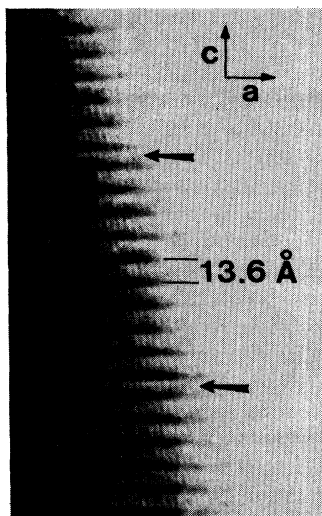


FIG. 3. A *b*-axis lattice image of the bulk 1:2:4 structure. In this image, planar defects corresponding to (002) layers with spacing smaller than 13.6 Å are seen (arrows), but most grains are perfect 1:2:4 structure without these defects.

ties of a 1:2:3 phase would be apparent in powder-diffraction patterns of the rare-earth-substituted samples. The 1:2:3 peak was seen only in the Sm and Nd patterns. All of the samples, with the exception of Nd, contained minor amounts of an unknown phase that has a characteristic diffraction peak at about 7.5 Å. Microanalyses of phases in the *R*-substituted systems are in progress.

Electron diffraction, TEM, and x-ray analytical electron microscopy (AEM) were performed with a Philips 420ST microscope equipped with an EDAX energy-dispersive detector and a PGT 4000 analyzer.¹⁴ Selected-area electron-diffraction patterns and AEM analyses from numerous grains of crushed sample confirm that most of the material is well-crystallized, bulk 1:2:4

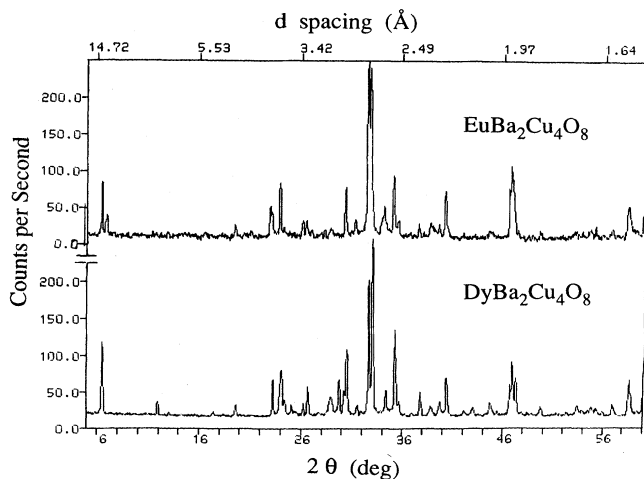


FIG. 4. X-ray powder diffraction patterns of $\text{EuBa}_2\text{Cu}_4\text{O}_8$ and $\text{DyBa}_2\text{Cu}_4\text{O}_8$. Note the (002) peak near $2\theta = 6.5^\circ$ (d spacing ≈ 13.6 Å) in both patterns, and the (004) peak of $\text{Eu}_2\text{Ba}_4\text{Cu}_7\text{O}_x$ near 7° (d spacing ≈ 12.55 Å).

structure. The data are consistent with the x-ray unit-cell parameters and space group *Ammm*. Single crystals of the yttrium 1:2:4 phase were observed up to several tens of μm across. Electron diffraction patterns (Fig. 2) indicate that most of this phase is rather well-ordered, though streaking parallel to \mathbf{c}^* shows that some crystals possess some structural disorder affecting the periodicity of the (00 $\bar{1}$) planes.

High-resolution lattice images (Fig. 3) show that at least part of the disorder results from the insertion of occasional layers that are either smaller or larger than the 13.6-Å (002) layers of the ideal 1:2:4 structure. Similar intergrowth defects have been observed in Bi and Tl based high- T_c superconductors, as well as in $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$.^{2,15} In the present material, a few ordered crystals of an additional pure Y-Ba-Cu phase with layer spacing of approximately 15.2 Å also were found. In addition to these complications related to layer spacing, electron-diffraction patterns and lattice images from 1:2:4 indicate that many crystals are ordered parallel to the *a* axis, producing modulations and superstructures in this direction having multiples of the 3.84-Å *a* axis repeat; the resulting microstructures will be described elsewhere.

X-ray-powder diffraction was performed on a Scintag automated powder diffraction using $\text{Cu } K\alpha$ radiation. Diffraction patterns of the samples were examined for evidence of the superconducting phases 1:2:4 and/or 1:2:3, as indicated by the presence of peaks at approximately 13.6 or 11.7 Å, respectively. For each sample that showed the 1:2:4 structure as the major phase, unit-cell parameters

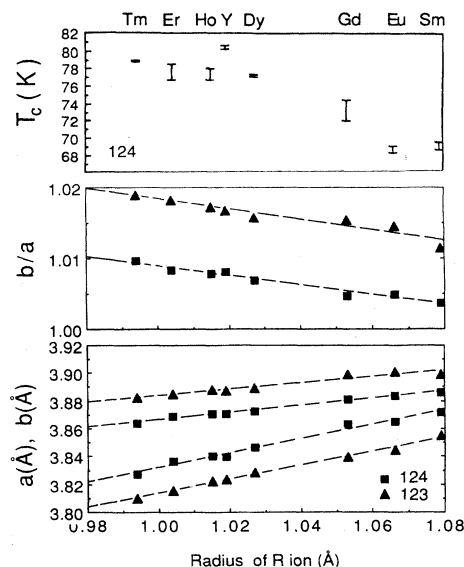


FIG. 5. T_c vs ion size, lattice parameters *a* and *b*, and orthorhombic distortion for 1:2:4 compounds (■) from Table I. Values for 1:2:3 compounds (▲) from Ref. 12. Ionic radii from Ref. 17; other data from Table I. In the 1:2:4 series T_c decreases with axial ratio *b/a* as ion size and *a* and *b* increase. In contrast, the 1:2:3 compounds show T_c 's increasing with ion size (Ref. 18) while distortion decreases. T_c of $\text{YBa}_2\text{Cu}_3\text{O}_8$ is ~ 3 K higher than $\text{HoBa}_2\text{Cu}_4\text{O}_8$, although lattice parameters are nearly identical (see text).

were refined by the Rietveld method, assuming space group *Ammm* and the model structure reported in Ref. 11. (In the cases of samples which also contained 1:2:3 or 2:4:7 phases, they were included in the refinement.) Our preliminary Rietveld studies indicate that the atomic structure of our 1:2:4 phases are consistent with that given in Ref. 11. Our lattice parameters are given in Table I. A detailed structural study giving atomic positions, lattice distortions, and anisotropic atomic vibrations has been performed on a single crystal of $\text{DyBa}_2\text{Cu}_4\text{O}_8$ (Ref. 16).

In the compounds containing larger¹⁷ (lighter) rare-earth ions, as *a* and *b* increase, T_c and orthorhombic distortion decrease (Fig. 5). In contrast, the 1:2:3 compound show T_c 's increasing with ion size¹⁸ and distortion decreasing.¹² This difference in behavior of T_c in closely related structures may provide a sensitive test of theoretical models. We also note that although the Ho and Y 1:2:4 compounds have nearly identical lattice parameters, the T_c of $\text{HoBa}_2\text{Cu}_4\text{O}_8$ is ~ 3 K lower. This may indicate that the large magnetic moment of Ho suppresses the coupling between the CuO_2 planes.

In the Eu and Gd systems, an additional 2:4:7 phase was found, with alternating 1:2:3 and 1:2:4 blocks joined at the *R* layers, analogous to $\text{Y}_2\text{Ba}_4\text{Cu}_7\text{O}_x$ (Ref. 19). Surprisingly, the T_c (~ 40 – 50 K) of this phase is much lower than the 70–90-K range of 1:2:3 and 1:2:4. It may be relevant that axial ratios ($b/a \approx 1.002$) are even smaller than in the corresponding 1:2:4 compounds. Diffraction peaks were found at about 12.6 \AA (see Fig. 4) which we interpret to be the 004 reflection of compounds with 2:4:7 structure. The lattice parameters of the 2:4:7 phase were determined by refining together with the 1:2:4 phase; results are given in Table I. The *c* axes of the 2:4:7 compounds are shorter than the sum of those of the corre-

sponding 1:2:4 and 1:2:3 compounds. We prepared the 2:4:7 phase in the Y, Dy, Ho, and Er systems as well, by varying the synthesis conditions.⁶

A unique feature of the 1:2:3 compound is the variable oxygen stoichiometry, and rapid and reversible oxidation-reduction above 400°C .²⁰ Varying the oxygen content changes T_c and the normal-state resistivity. An absence of variable oxygen stoichiometry in 1:2:4 was conjectured by Marsh *et al.*,¹¹ on the basis that each oxygen in the two CuO layers of 1:2:4 is bonded to three Cu ions, in contrast to 1:2:3 where the O is bonded to only two Cu ions. Preliminary thermogravimetric studies indicate that $\text{YBa}_2\text{Cu}_4\text{O}_8$ indeed lacks the variable oxygen stoichiometry of $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$. Structural studies¹⁶ indicate that the oxygen double-chain sites are fully occupied. The consistent oxygen content should permit precise determination of differences of T_c caused by varying rare-earth magnetic moment as well as ion size. The twinning caused by the tetragonal-orthorhombic transition during cooling of 1:2:3 should be absent, so 1:2:4 may be technologically useful.

The authors thank C. G. Hadidiacos for assistance in microprobe analysis, Daphne Ross for assistance with x-ray diffraction, R. N. Shelton and J. L. Peng for access to and assistance with superconducting quantum interference device (SQUID) susceptometer and x-ray diffractometer, G. W. Smith for useful advice, and M. T. Tran and N. A. Crocker for laboratory assistance. Work at the Geophysical Laboratory was supported by National Science Foundation (NSF) Grants No. EAR8419982 and No. EAR8618602; work at Johns Hopkins University by NSF Grant No. EAR8609227. D.E.M. wishes to express his appreciation for the encouragement and support of L. W. Alvarez, R. A. Muller, and P. J. Oddone.

- ¹C. Michel *et al.*, *Z. Phys. B* **68**, 421 (1987); M. Maeda *et al.*, *Jpn. J. Appl. Phys. Lett.* **27**, L209 (1988); R. M. Hazen *et al.*, *Phys. Rev. Lett.* **60**, 1174 (1988); T. M. Shaw *et al.*, *Phys. Rev. B* **37**, 16 (1988); J. B. Torrance *et al.*, *Solid State Commun.* **66**, 703 (1988); J. M. Tarascon *et al.*, *Phys. Rev. B* **37**, 9382 (1988); S. A. Sunshine *et al.*, *ibid.* **38**, 893 (1988).
²D. R. Veblen *et al.*, *Nature (London)* **332**, 334 (1988).
³Z. Z. Sheng and A. M. Hermann, *Nature (London)* **332**, 55 (1988); R. M. Hazen *et al.*, *Phys. Rev. Lett.* **60**, 1657 (1988); M. A. Subramanian *et al.*, *Science* **239**, 1015 (1988); C. C. Torardi *et al.*, *ibid.* **240**, 1015 (1988).
⁴S. S. P. Parkin *et al.*, *Phys. Rev. Lett.* **61**, 750 (1988).
⁵Morris Research, 1862 Euclid Ave., Berkeley CA 94709.
⁶D. E. Morris *et al.*, Lawrence Berkeley Laboratory Report No. LBL-26250, 1988 (unpublished).
⁷M. P. A. Viegers *et al.*, *J. Mater. Res.* **2**, 743 (1987); J. Narayan *et al.*, *Appl. Phys. Lett.* **51**, 940 (1987).
⁸H. W. Zandbergen *et al.*, *Nature (London)* **331**, 596 (1988).
⁹A. F. Marshall *et al.*, *Phys. Rev. B* **37**, 9353 (1988).
¹⁰J. Kwo *et al.*, *Appl. Phys. Lett.* **52**, 1625 (1988); K. Char *et al.*, *Phys. Rev. B* **38**, 834 (1988); M. L. Mandich *et al.*, *ibid.*

38, 5031 (1988).

- ¹¹P. Marsh *et al.*, *Nature (London)* **334**, 141 (1988).
¹²J. M. Tarascon *et al.*, *Phys. Rev. B* **36**, 226 (1987).
¹³M. J. Drake and D. F. Weill, *Chem. Geol.* **10**, 179 (1972).
¹⁴K. J. T. Livi and D. R. Veblen, *Am. Mineral.* **72**, 113 (1987); D. R. Veblen and D. L. Bish, *ibid.* **73**, 667 (1988).
¹⁵R. M. Hazen *et al.*, *Phys. Rev. Lett.* **60**, 1174 (1988); **60**, 1657 (1988); A. Ourmazd *et al.*, *Nature (London)* **327**, 308 (1987).
¹⁶R. M. Hazen, L. W. Finger, and D. E. Morris, *Appl. Phys. Lett.* **54**, 1057 (1989).
¹⁷R. D. Shannon, *Acta Crystallogr. A* **32**, 751 (1976).
¹⁸B. Dabrowski and D. G. Hinks, in *Proceedings of the Second Annual Conference on Superconductivity and Its Applications, Buffalo, 1988*, edited by H. S. Kwok and D. T. Shaw (Elsevier, New York, 1988), p. 141.
¹⁹P. Bordet *et al.*, *Nature (London)* **334**, 596 (1988).
²⁰D. E. Morris *et al.*, *Proceedings of the Symposium of High Temperature Superconductors*, edited by D. U. Gubser and M. Schluter (Materials Research Society, Pittsburgh, 1987), Vol. EA-11, p. 209.

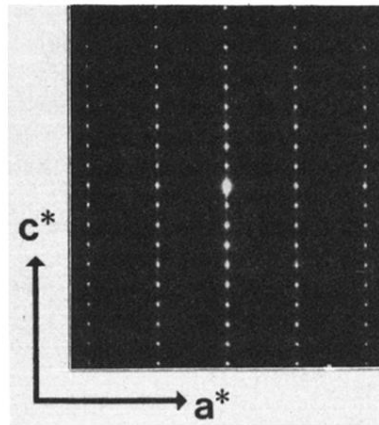


FIG. 2. A b -axis selected-area electron diffraction pattern of $\text{YBa}_2\text{Cu}_4\text{O}_8$, indicating that most of this phase is well ordered. Minor diffuse streaking parallel to c^* indicates that some crystals possess some structural disorder affecting the periodicity of the $(00\bar{1})$ planes (see Fig. 3).

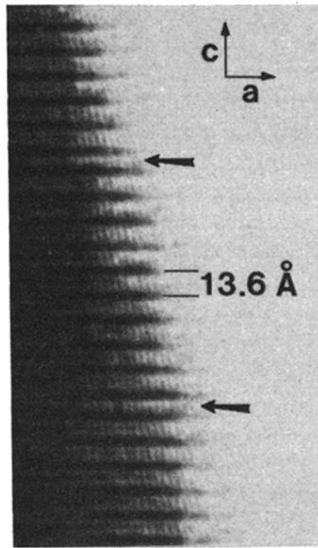


FIG. 3. A **b**-axis lattice image of the bulk 1:2:4 structure. In this image, planar defects corresponding to (002) layers with spacing smaller than 13.6 Å are seen (arrows), but most grains are perfect 1:2:4 structure without these defects.